

Orbital-selective Mass Enhancements in Multi-band $\text{Ca}_{2-x}\text{Sr}_x\text{RuO}_4$ Systems Analyzed by the Extended Drude Model

J. S. Lee,¹ S. J. Moon,¹ T. W. Noh¹, S. Nakatsuji,² and Y. Maeno^{2,3}
¹*ReCOE & School of Physics, Seoul National University, Seoul 151-747, Korea*
²*Department of Physics, Kyoto University, Kyoto 606-8502, Japan*
³*International Innovation Center, Kyoto University, Kyoto 606-8501, Japan*

We investigated optical spectra of quasi-two-dimensional multi-band $\text{Ca}_{2-x}\text{Sr}_x\text{RuO}_4$ systems. The extended Drude model analysis on the ab-plane optical conductivity spectra indicates that the effective mass should be enhanced near $x = 0.5$. Based on the sum rule argument, we showed that the orbital-selective Mott-gap opening for the $d_{yz/zx}$ bands, the widely investigated picture, could not be the origin of the mass enhancement. We exploited the multi-band effects in the extended Drude model analysis, and demonstrated that the intriguing heavy mass state near $x = 0.5$ should come from the renormalization of the d_{xy} band.

PACS numbers: 78.20.-e, 78.30.-j, 78.40.-q, 71.30.+h

The Mott metal-insulator transition has been one of major topics in condensed matter physics for many years. It is well known that the conduction electron mass could be enhanced in metals due to strong electron correlations, and that it should diverge toward a metal-insulator transition. Through Brinkman and Rice, such a mass divergence has been predicted to occur in bandwidth controlled systems, where the ratio between the interaction strength U and the bandwidth W can be varied for a fixed band filling [1]. Recently, it has been shown that the iso-electronic $\text{Ca}_{2-x}\text{Sr}_x\text{RuO}_4$ (CSRO) compounds comprise an excellent system to investigate the W -controlled Mott metal-insulator transition [2, 3, 4, 5]. Here W for the Ru t_{2g} states should keep decreasing due to the internal chemical pressure from substituting the Sr^{2+} ion with the smaller Ca^{2+} ion, which gives rise to a transition from a multi-band metal ($x=2.0$) to a Mott-insulator ($x=0.0$). Contrary to the simple expectation of the gradual change in W with x , these compounds exhibit quite unusual behavior near $x=0.5$. While the metal-insulator transition occurs for $x<0.2$, anomalous enhancements of magnetic susceptibility $\chi(0)$ and specific heat coefficient γ , indicating a heavy mass state, were observed near $x=0.5$ [2, 4].

In order to explain these surprising experimental behaviors, numerous workers have paid attention to the directional dependences of the Ru t_{2g} orbitals [6, 7, 8, 9, 10]. Due to the planar crystal structure of the layered perovskite, partially filled t_{2g} bands become separated into a two-dimensional d_{xy} band, and two nearly one-dimensional $d_{yz/zx}$ bands. Since the d_{xy} band at $x=2.0$ has a wider W than the $d_{yz/zx}$ bands, some workers have argued that orbital-selective Mott transition (OSMT) could occur successively: i.e., at $x=0.5$ for the $d_{yz/zx}$ bands and at $x<0.2$ for the d_{xy} band [7, 8]. However, other workers insisted that the Mott transitions should occur simultaneously for $x<0.2$ [9]. The intriguing picture of OSMT has been the subject of heated debate, but no consensus has been reached yet [10].

Optical spectroscopy has been used as a power-

ful method to investigate metal-insulator transitions of strongly correlated electron systems. Especially, the extended Drude model (EDM) has been extensively used to explain the electrodynamic responses near metal-insulator transitions of numerous correlated electron systems, such as heavy fermion compounds [11] and high transition temperature superconductors [12]. This phenomenological theory describes optical conductivity spectra $\tilde{\sigma}(\omega) [= \sigma_1(\omega) + i\sigma_2(\omega)]$ of free carriers in terms of the frequency(ω)-dependent scattering rate $1/\tau(\omega)$ and the mass enhancement $\lambda(\omega)$ (effective mass $m^*(\omega)$ normalized by the band mass m_b), which is given as

$$\lambda(\omega) = \frac{\omega_p^2}{4\pi} \cdot \frac{\sigma_2(\omega)}{|\tilde{\sigma}(\omega)|^2}. \quad (1)$$

Here, ω_p is the plasma frequency. However, it should be noted that the free carriers in this model were assumed to originate from a single band. Up to this point, there have been no efforts to extend this analysis to the multi-band metallic compounds.

Even for a multi-band system, $\tilde{\sigma}(\omega)$ is an averaged response for all k -space. It contains all the contributions from each independent band, so it should be expressed as a linear addition of such contributions. As a result, the optical sum rule should be valid for the multi-band system, and the total spectral weight of the coherent peak ω_p^2 should be $\omega_p^2 = \sum_i \omega_{p,i}^2$. By expressing the contribution from each band in terms of EDM and comparing the sum with Eq. (1), we obtained $\lambda(\omega) = \sum_i \omega_{p,i}^2 \sum_i \omega_{p,i}^2 \tau_i^2(\omega) \lambda_i(\omega) / (\sum_i \omega_{p,i}^2 \tau_i(\omega))^2$. When all of τ_i are nearly the same [13], $\lambda(\omega)$ obtained from Eq. (1) corresponds approximately to the averaged value of contributions from each band weighted by $\omega_{p,i}^2$, i.e.,

$$\lambda(\omega) \simeq \sum_i \omega_{p,i}^2 \lambda_i(\omega) / \sum_i \omega_{p,i}^2. \quad (2)$$

For the CSRO system, superscripts α and β are commonly used to indicate two bands formed by the d_{yz}

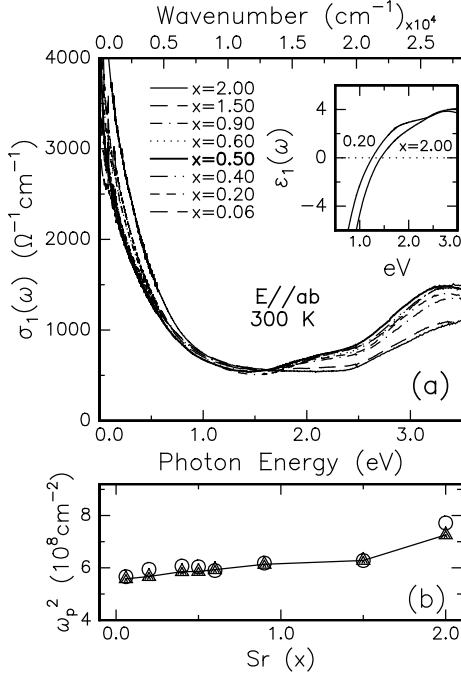


FIG. 1: (a) x -dependent $\sigma_1(\omega)$ of $\text{Ca}_{2-x}\text{Sr}_x\text{RuO}_4$ at room temperature. Spectral weight redistribution occurs around 1.5 eV. Inset shows $\varepsilon_1(\omega)$ of the $x=2.00$ and 0.20 compounds. (b) x -dependent changes of ω_p^2 . The solid and open symbols represent values of ω_p^2 obtained by the integration of $\sigma_1(\omega)$ and the zero-crossing of $\varepsilon_1(\omega)$, respectively.

and the d_{zx} orbital states. And let us assign the $d_{yz/zx}^\alpha$, $d_{yz/zx}^\beta$, and d_{xy} bands as $i = 1, 2$, and 3 , respectively.

In this Letter, we investigated the doping-dependent in-plane $\tilde{\sigma}(\omega)$ taking into account of the multi-band effects. Based on the sum rule, we could argue that the controversial $d_{yz/zx}$ bands would not experience the OSMT. Instead, we could demonstrate that the heavy mass state should be contributed to by a strong renormalization of the d_{xy} band. We will provide additional indirect evidence for this intriguing picture from the x -dependent changes of $p-d$ charge transfer excitations.

High quality CSRO single crystals were grown by the floating zone method [14]. Near-normal incident reflectivity spectra were measured in a photon energy range between 5 meV and 30 eV. Using the Kramers-Kronig analysis, $\tilde{\sigma}(\omega)$ were obtained [15].

Figure 1 shows the doping-dependent ab-plane $\sigma_1(\omega)$ of CSRO ($0.06 \leq x \leq 2.0$) at room temperature. All of the $\sigma_1(\omega)$ curves show strong coherent peaks in the zero frequency limit. While the simple Drude model cannot explain the ω -dependence of these $\sigma_1(\omega)$, application of the EDM would be useful to get information about the changes of electrodynamic parameters.

Before going into a detailed discussion about the mass enhancement changes in CSRO using Eq. (1), it is worthwhile to mention how we obtained ω_p values. First, we

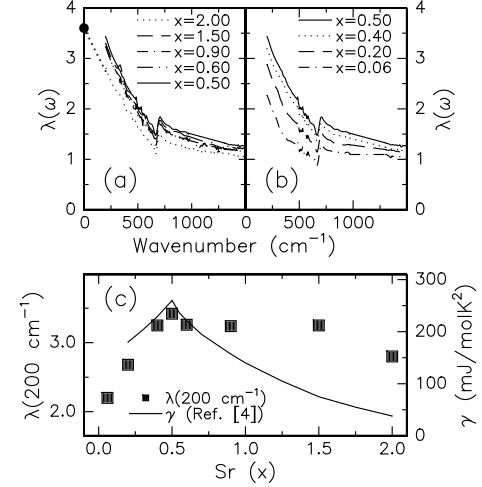


FIG. 2: $\lambda(\omega)$ of $\text{Ca}_{2-x}\text{Sr}_x\text{RuO}_4$ at room temperature obtained by extended Drude model analysis for ($0.5 \leq x \leq 2.0$) (a) and for ($0.06 \leq x \leq 0.5$) (b). As x decreases from 2.0, $\lambda(\omega)$ increases initially, reaches a maximum at $x=0.5$, and then decreases. (c) x -dependence of $\lambda(200 \text{ cm}^{-1})$ and γ , the latter of which is quoted from Ref. [4]. Note that the enhancement of $\lambda(200 \text{ cm}^{-1})$ at $x=0.5$ is similar to that of γ . However, its magnitude is much smaller.

estimated ω_p by integrating the spectral weight of the coherent peak using $\omega_p^2 = 8 \int_0^{\omega_c} \sigma_1(\omega) d\omega$. Here, ω_c is the highest cutoff frequency for the free carrier response. As shown in Fig. 1(a), an isosbetic point exists around 1.5 eV: as x decreases, the spectral weight below 1.5 eV decreases, but that of the higher energy region increases. So, we chose ω_c as 1.5 eV. The x -dependent values of ω_p^2 are displayed as solid triangles in Fig. 1(b), where ω_p^2 keeps decreasing down to $x=0.06$. Second, we determined ω_p^2 from $\varepsilon_1(\omega)$ [$=\varepsilon_\infty - 4\pi\sigma_2(\omega)/\omega$] using the relation $\varepsilon_1(\omega_p/\sqrt{\varepsilon_\infty}) = 0$. $\varepsilon_1(\omega)$ for two representative metallic compounds, i.e., $x=2.00$ and 0.20 , are shown in the inset of Fig. 1(a). They show monotonic ω -dependent increases crossing a zero level around 1.3 eV. By adopting $\varepsilon_\infty = 5.8$, we estimated ω_p^2 and displayed them as open circles in Fig. 1(b), which show behavior quite similar to that of the solid triangles. For further discussion in this paper, we will adopt the ω_p^2 values estimated by the first method.

Figures 2(a) and 2(b) show the results for $\lambda(\omega)$ obtained from Eq. (1). As x decreases, the $\lambda(\omega)$ curves show a small upward shift down to $x=0.5$ [Fig. 2(a)], and then they exhibit a rather significant downward shift below $x=0.5$ [Fig. 2(b)]. Figure 2(c) shows the x -dependent changes of $\lambda(\omega)$ at the low frequency limit, i.e., 200 cm^{-1} , which displays a peak near $x=0.5$ [16]. This x -dependent change is reminiscent of the enhancement of γ shown as a solid line in Fig. 2(c) [4]. These unusual behaviors suggest that the Fermi surface topologies must experience anomalies near $x=0.5$.

The de Haas-van Alphen (dHvA) measurement could

be a very powerful tool to investigate Fermi surface topologies of very pure samples. Mackenzie *et al.* performed the dHvA measurements on Sr_2RuO_4 [17]. They observed quantum oscillations coming from three t_{2g} bands, two from the $d_{yz/zx}$ bands and one from d_{xy} band. They found that $n_1:n_2:n_3 \simeq 1:1:1$ and $m_{b,1}:m_{b,2}:m_{b,3} \simeq 1:2:3$, where n_i is the free carrier density of the i -th band. Since $\omega_p^2 = 4\pi n e^2 / m_b$, $\omega_{p,1}^2:\omega_{p,2}^2:\omega_{p,3}^2 \simeq 6:3:2$. And, they also reported that $\lambda_1(0):\lambda_2(0):\lambda_3(0) \simeq 3.3:3:4$. From these values, we can estimated $\lambda(0)$ as 3.3 from Eq. (2). This value is well consistent with the optically observed value (~ 3.5), shown as the solid circle on the y-axis of Fig. 2(a), demonstrating the validity of our EDM analysis for the multi-band system.

On the other hand, angle-resolved photoemission spectroscopy (ARPES) studies could be another way to look into the Fermi surface. Recently, Wang *et al* performed ARPES measurements on an $x=0.5$ sample, and showed that its Fermi surface topology remains nearly the same as that of an $x=2.0$ sample [10]. They claimed that the OSMT should not occur in the CSRO system. The photoemission studies are generally sensitive to the surface (not to the bulk), and the ARPES study could not explain why the heavy mass state does exist near the $x=0.5$ sample.

Optical spectroscopy could provide new insights on OSMT of the CSRO system. We will test the model of the OSMT in the $d_{yz/zx}$ bands, which is a seemingly fascinating and the most widely investigated scenario [7, 8] to explain the anomalous heavy mass state around $x=0.5$ [4]. Using the dHvA measurement results [17], the ratio between $\omega_{p,3}^2$ and $(\omega_{p,1}^2 + \omega_{p,2}^2)$ for $x=2.0$ could be estimated to be about $1/4.5$. If the $d_{yz/zx}$ bands open a Mott gap, the optical sum rule states that the reduction in ω_p^2 should reach around 82 % of ω_p^2 . However, as shown in Fig. 1(b), ω_p^2 for $x=0.5$ decreases only by ~ 20 %. Such a difference in the reduction of ω_p^2 clearly demonstrates that the Mott-gap opening could not occur in the narrow $d_{yz/zx}$ bands.

What should be responsible for the unusual behavior near $x=0.5$? It should be noted that the enhancement of γ between the $x=2.0$ and the $x=0.5$ samples is about 6.0, significantly higher than the corresponding value (i.e. 1.4) of $\lambda(200 \text{ cm}^{-1})$ [See Fig. 2(c)]. This difference comes from how the mass enhancement of each band can contribute to the total responses of γ and λ in the multi-band CSRO system. The specific heat coefficient γ can be written as a linear summation of contributions from three t_{2g} bands, i.e., $\gamma = \sum_i \gamma_i$. On the other hand, $\lambda(\omega)$ obtained from Eq. (1) should be the averaged value of mass enhancement contributions, weighted by $\omega_{p,i}^2$, as shown in Eq. (2). As an illustration, let us consider a simple multi-band system with three bands, whose plasma frequencies and masses are exactly the same. If one of the bands experiences a mass enhancement of 16 times, we can estimate that the total specific heat can be enhanced

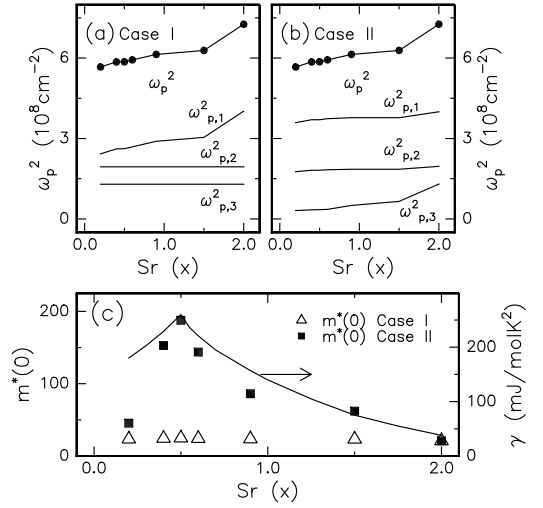


FIG. 3: (a) Proposed changes of ω_p^2 for Case I, where only one of the $d_{yz/zx}$ bands experience a reduction in spectral weight. (b) Proposed changes of ω_p^2 for Case II, where the d_{xy} band experiences a significant spectral weight change. (c) The estimated $m^*(0)$ for each case. The solid line is the specific heat data from Ref. [4]. The good agreement between Case II and γ indicates that the mass renormalization near the $x=0.5$ sample should occur mostly in the d_{xy} band.

by 6 times. And from Eq. (2), assuming $m_b = m^*$, that the average λ can be enhanced by only about 1.5 times. In a real system, ω_p^2 and $\lambda(\omega)$ of each band cannot be the same. However, using a similar argument with proper guidance, we will be able to unveil the nature of the heavy mass state near the $x=0.5$ CSRO sample.

First, let us assume one limiting case (Case I), where $\omega_{p,1}^2$ would decrease with x , while $\omega_{p,2}^2$ and $\omega_{p,3}^2$ remain the same as those at $x=2.0$. This limiting case is illustrated in Fig. 3(a). Using Eq. (2), $\omega_{p,i}^2 = 4\pi n_i e^2 / m_{b,i}$ and $\lambda_i(0) = m_i^*(0) / m_{b,i}$, we could evaluate $m_i^*(0)$ [18], assuming the carrier densities n_i of each band would not change with x [10]. As shown in Fig. 3(c), $m^*(0) [\equiv m_1^*(0) + m_2^*(0) + m_3^*(0)]$ cannot be significantly enhanced, failing to explain the specific heat data. The reduction of $\omega_{p,2}^2$ gives a similar result with that of Case I. Second, let us consider the other limiting case (Case II), where the d_{xy} band would experience a significant change with x [19], which is illustrated in Fig. 3(b). Using a similar process, we could evaluate $m^*(0)$. As shown with the solid squares in Fig. 3(c), $m^*(0)$ enhances from 21 at $x=2.0$ to around 200 at $x=0.5$, and then decreases for $x<0.5$. This change of $m^*(0)$ can explain that of γ quite well. Our EDM analysis based on the multi-band extension indicates that the heavy mass state around $x=0.5$ should be contributed to by the renormalization of the d_{xy} band. It is quite interesting that the d_{xy} band, having a larger W than the $d_{yz/zx}$ bands, could be strongly renormalized near $x=0.5$.

Finally, let us discuss how the d_{xy} band could be renor-

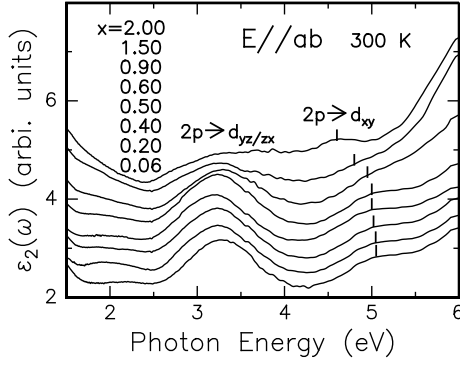


FIG. 4: x -dependent ab-plane $\varepsilon_2(\omega)$ of the $\text{Ca}_{2-x}\text{Sr}_x\text{RuO}_4$ compounds. Two peaks around 3.3 and 4.7 eV correspond to the transitions from the O $2p$ band to the Ru $d_{yz/zx}$ and the Ru d_{xy} band, respectively. The x -dependent positions of the higher energy peak are indicated with vertical solid lines. The shift of this O $2p \rightarrow$ Ru d_{xy} peak indicates that the d_{xy} band experience significant electronic structural changes above $x=0.5$.

malized and give rise to a large m^* near $x=0.5$. Figure 4 shows x -dependent changes of $\varepsilon_2(\omega)$ $[=4\pi\sigma_1(\omega)/\omega]$ from 1.5 eV to 6 eV. For the $x=2.0$ compound, there are multi-peak structures around 3.5 and 4.7 eV. For the metallic CSRO compounds, the RuO_6 octahedra are largely elongated along the c -axis [3]. This leads to a stronger hybridization of the d_{xy} band with the O $2p$ band than that of the $d_{yz/zx}$ bands, and results in the higher energy position of the $p-d$ transition to the d_{xy} band [20]. So, the peaks around 3.5 and 4.7 eV can be attributed to the charge-transfer transitions from the O $2p$ band to the unoccupied Ru $d_{yz/zx}$ bands and to the Ru d_{xy} band, respectively. As x decreases down to $x=0.5$, the lower energy peak does not experience a discernible change. However, the higher energy peak shows a strong blue shift, indicating that the unoccupied band having the d_{xy} character must be shifted to a higher energy away from the Fermi energy. These changes could result in smaller contribution of d_{xy} band to the metallic response and lead to the enhancement of its $m^*(0)$ near $x=0.5$. From the neutron scattering experiments [3], it is well known that a rotation of the RuO_6 octahedra along the c -axis increases from around $x=1.5$ and saturates below $x=0.5$. In this respect, the observed evolution of the d_{xy} band could be attributed to the RuO_6 rotation [21]. The detailed mechanism should be elucidated in future work [22].

In summary, we addressed the evolution of electronic structures in multi-band $\text{Ca}_{2-x}\text{Sr}_x\text{RuO}_4$ by investigating the optical spectra. The argument based on the optical sum rule revealed that $d_{yz/zx}$ bands should remain itinerant near $x=0.5$. Using the extended Drude model analysis, we found that the Fermi surface topologies should experience anomalies near $x=0.5$, and we proposed that

the heavy mass state near $x=0.5$ should come from a strong renormalization of the d_{xy} band.

We acknowledge the Pohang Advanced Light Source for allowing us to use some of their facilities. This work was supported by the Ministry of Science and Technology through the Creative Research Initiative program and in part by Grants-in-Aid for Scientific Research from JSPS of Japan.

-
- [1] W. F. Brinkman and T. M. Rice, Phys. Rev. B **2**, 4302 (1970).
 - [2] S. Nakatsuji and Y. Maeno, Phys. Rev. Lett. **84**, 2666 (2000); S. Nakatsuji and Y. Maeno, Phys. Rev. B **62**, 6458 (2000).
 - [3] O. Friedt *et al.*, Phys. Rev. B **63**, 174432 (2001).
 - [4] S. Nakatsuji *et al.*, Phys. Rev. Lett. **90**, 137202 (2003).
 - [5] S. Nakatsuji *et al.*, Phys. Rev. Lett. **93**, 146401 (2004).
 - [6] Z. Fang and K. Terakura, Phys. Rev. B **64**, 020509 (2001).
 - [7] V. I. Anisimov *et al.*, Eur. Phys. J. B **25**, 191 (2002).
 - [8] A. Koga *et al.*, Phys. Rev. Lett. **92**, 216402 (2004).
 - [9] A. Liebsch, Phys. Rev. Lett. **91**, 216401 (2003); A. Liebsch, Euro. Phys. Lett. **63**, 97 (2003).
 - [10] S.-C. Wang *et al.*, Phys. Rev. Lett. **93**, 177007 (2004).
 - [11] P. E. Sulewski *et al.*, Phys. Rev. B **38**, 5338 (1988).
 - [12] A. V. Puchkov, D. N. Basov, and T. Timusk, J. Phys.: Condens. Matter **8**, 10049 (1996).
 - [13] For Sr_2RuO_4 , $\tau_i(0)$ are known to be nearly the same. [See S.-C. Wang *et al.*, Phys. Rev. Lett. **91**, 137002 (2004).] Even though τ_i values for each band are different by a factor of 3, the results shown in Fig. 3(c) was found to remain nearly the same.
 - [14] S. Nakatsuji and Y. Maeno, J. Solid State Chem. **156**, 26 (2001).
 - [15] J. S. Lee *et al.*, Phys. Rev. Lett. **89**, 257402 (2002).
 - [16] We obtained the optical spectra at 10 K for the $x=2.0$, 0.5, and 0.2 compounds, and found that the behaviors at 10 K are similar with those at room temperature.
 - [17] A. P. Mackenzie *et al.*, Phys. Rev. Lett. **76**, 3786 (1996).
 - [18] $\lambda(0)$ for each x is linearly extrapolated from the value at 200 cm^{-1} as for the case $x=2.0$ shown in Fig. 2(a). And, x -dependent $m_1^*(0)$, $m_2^*(0)$, and $m_3^*(0)$ are normalized as they should be to 3, 6, and 12, respectively, at $x=2.0$ [17].
 - [19] If we assumed that the spectral change with x might be solely attributed to the d_{xy} band, we found negative values of ω_p^2 below $x=0.9$. So we considered that the $d_{yz/zx}$ bands also have small changes, while the main spectral changes should come from the change of the d_{xy} band.
 - [20] J. S. Lee *et al.*, Phys. Rev. B **70**, 085103 (2004).
 - [21] Figure 3(c) shows that the estimated $m^*(0)$ values in Case II agree quite well with the experimental γ values for the samples with $x \geq 0.5$. However, there are some deviations for the samples with $x < 0.5$. This deviation could be attributed to the tilting of the RuO_6 octahedra, which would provide additional increase of γ [3].
 - [22] There are some photoemission data to support this RuO_6 rotation picture by B. J. Kim *et al.*, (private communication).